

Thermal conductivity of $R_2\text{CuO}_4$, with $R = \text{La}, \text{Pr}$ and Gd

K. Berggold ^{a,*}, T. Lorenz ^a, J. Baier ^a, M. Kriener ^a, D. Senff ^a, S. Barilo ^b
and A. Freimuth ^a

^a*II. Physikalisches Institut, Universität zu Köln, 50937 Köln, Germany*

^b*Institute of Solid State & Semiconductor Physics, Belarussian Academy of Sciences, Minsk 220072, Belarus*

Abstract

We present measurements of the in-plane (κ_{ab}) and out-of-plane (κ_c) thermal conductivity of Pr_2CuO_4 and Gd_2CuO_4 single crystals. The anisotropy gives strong evidence for a large contribution of magnetic excitations to κ_{ab} , i.e. for a heat current within the CuO_2 planes. However, the absolute values of κ_{mag} are lower than previous results on La_2CuO_4 . These differences probably arise from deviations from the nominal oxygen stoichiometry. This has a drastic influence on κ_{mag} , which is shown by an investigation of a $\text{La}_2\text{CuO}_{4+\delta}$ polycrystal.

Key words: Thermal conductivity, low-dimensional quantum spin systems

PACS: 74.72.-h, 66.70.+f, 75.10.Jm

One peculiarity of low-dimensional spin systems is the possibility of large contributions to the heat transport by magnetic excitations. This has been found in 1D systems like spin ladders,[1] whereas the situation in 2D is less clear. The CuO_2 planes in La_2CuO_4 are a good realization of a 2D antiferromagnetic Heisenberg square lattice with a large exchange constant $J \approx 1400$ K.[2] The thermal conductivity of La_2CuO_4 shows an unusual behavior.[3] For a heat current along the c direction one low-temperature maximum is present, as it is expected for an insulator. The heat is carried by acoustic phonons, and for high temperatures Umklapp scattering yields an approximate $1/T$ behavior of κ_c . However, for a heat current parallel to the CuO_2 planes a second broad maximum arises in addition to the low-temperature maximum. This can be interpreted in terms of an additional contribution to the heat transport by magnetic excitations. Depending on the crystals, values of $\kappa_{\text{mag}}^{(300\text{ K})} \approx 15 \dots 24$ W/Km are reported.[3,4,5] However, a double peak of κ could also arise from a suppression acting in a certain tempera-

ture window.[6] This requires an additional scattering mechanism, e.g. due to a structural instability, which is present in La_2CuO_4 . [7] Such a structural instability is not present in the nearly iso-structural compound $\text{Sr}_2\text{CuO}_2\text{Cl}_2$, but still there is a second maximum of κ_{ab} . [8] This gives evidence for a magnetic origin of the second maximum and suggests that a magnetic contribution to κ_{ab} could be a common feature of all single-layered insulating cuprates. In order to investigate this, we studied κ of $R_2\text{CuO}_4$, with $R = \text{Pr}, \text{Gd}$. Both compounds have a very similar CuO_2 square lattice and exchange constant as La_2CuO_4 . [9] However, for $R = \text{Pr}$ the structure is stable down to lowest temperatures, whereas for $R = \text{Gd}$ a structural phase transition occurs at 685 K. [10]

Fig. 1a shows κ_{ab} and κ_c for Pr_2CuO_4 . For κ_c we observe one low-temperature maximum and a $1/T$ behavior (solid line) above about 70 K. For κ_{ab} , however, a pronounced shoulder occurs at high temperatures, which leads to an anisotropy $\kappa_{ab}/\kappa_c \approx 2$ at room temperature, whereas the heights of the low-temperature maxima differ only by 20 %. For Gd_2CuO_4 (Fig. 1b), κ_c can also be described well by phonons. For κ_{ab} a second broad maximum arises at high temperatures. The

* Corresponding author. Tel: +49-221-470-2911 fax: +49-221-470-6708

Email address: berggold@ph2.uni-koeln.de (K. Berggold).

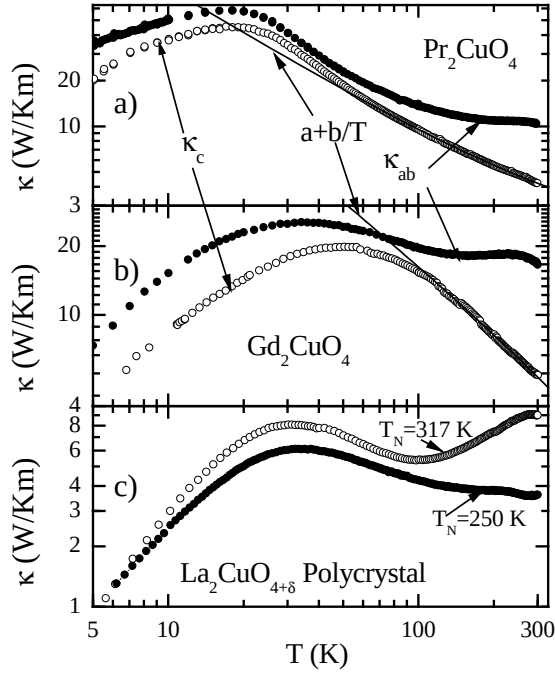


Fig. 1. Panel a) and b): κ_{ab} and κ_c for Pr_2CuO_4 and Gd_2CuO_4 . The phononic behavior of the out-of-plane measurements at high temperatures is confirmed with $1/T$ fits (lines). Panel c): κ of a $\text{La}_2\text{CuO}_{4+\delta}$ polycrystal, see text.

anisotropy at room temperature $\kappa_{ab}/\kappa_c \approx 3$ is even larger than for Pr_2CuO_4 . The low-temperature maxima differ by about 25 % in height. They are shifted in temperature, which is likely to be caused by sheet defects, which are more efficient for κ_c . This anisotropic behavior, which occurs in both compounds independently from the presence of a structural phase transition, gives further evidence that a magnetic contribution to κ_{ab} is a general feature of these cuprates. We estimate the magnetic contribution at room temperature from the difference $\kappa_{\text{mag}} = \kappa_{ab} - \kappa_c$. This assumes that the phononic anisotropy is not too big, what is reasonable, since the low-temperature maxima for the different directions differ much less than the room-temperature values. In this way, we get $\kappa_{\text{mag}}^{(300\text{ K})} \approx 6\text{ W/Km}$ for Pr_2CuO_4 and $\approx 11\text{ W/Km}$ for Gd_2CuO_4 .

The different values of $\kappa_{\text{mag}}^{(300\text{ K})}$ raise the question, what determines the size of κ_{mag} . Because J does not differ too much, it is reasonable to assume that the differences mainly arise from different scattering of the heat-carrying excitations. Possible scattering mechanisms are magnon-magnon, magnon-phonon and magnon-hole scattering. Because of the similar magnetic subsystem for all these compounds, we do not expect that magnon-magnon scattering is very different. Whether a different magnon-phonon scattering is present, is difficult to judge at the present stage of the available data. Thus, we concentrate on the study

of magnon-hole scattering. The antiferromagnetic order in $\text{La}_2\text{CuO}_{4+\delta}$ is suppressed drastically by hole doping. To investigate the increase of the magnon-hole scattering, we measured κ of a $\text{La}_2\text{CuO}_{4+\delta}$ polycrystal (Fig. 1c), which was annealed either in oxygen ($T_N = 250\text{ K}$) or in vacuum ($T_N = 317\text{ K}$). For $T_N = 317\text{ K}$ a pronounced high-temperature maximum is present. The magnitude of this maximum is lower than observed in single crystals, which partly arises from the averaging $\kappa = 1/3\kappa_c + 2/3\kappa_{ab}$ in a polycrystal. Moreover, T_N is still lower than the maximum value $T_N^{\text{max}} \approx 325\text{ K}$. [11] Weak oxygen doping is also the most probable reason for the different $\kappa_{\text{mag}}^{(300\text{ K})}$ in single crystals. [3,4,5] On our Pr_2CuO_4 and Gd_2CuO_4 crystals we determined $T_N = 250\text{ K}$ and 295 K from neutron scattering and magnetic susceptibility data, respectively. For Gd_2CuO_4 we are not aware of higher T_N values, but for Pr_2CuO_4 significantly larger values up to $T_N \approx 270\text{ K}$ are reported. [9] This may explain the low value of κ_{mag} for Pr_2CuO_4 . However, T_N is not solely determined by the oxygen content, but also depends e.g. on the magnetic anisotropy. Thus, no direct conclusion concerning the hole content can be drawn from a comparison of T_N for $R_2\text{CuO}_4$ with different R .

In conclusion, we have measured κ_{ab} and κ_c of Pr_2CuO_4 and Gd_2CuO_4 . The temperature dependence of κ_{ab} and the anisotropy κ_{ab}/κ_c give evidence for a magnetic contribution to κ_{ab} and suggest that this behavior is a common feature of single-layered cuprates. The magnetic contribution is suppressed drastically by charge-carrier doping, which was shown on a $\text{La}_2\text{CuO}_{4+\delta}$ polycrystal.

This work was supported by the Deutsche Forschungsgemeinschaft through SFB 608.

References

- [1] A. V. Sologubenko *et al.*, Phys. Rev. Lett. **84**, 2714 (2000).
- [2] M. A. Kastner *et al.*, Rev. Mod. Phys. **70**, 897 (1998).
- [3] Y. Nakamura *et al.*, Physica C **185-189**, 1409 (1991).
- [4] J.-Q. Yan *et al.*, Phys. Rev. B **68**, 104520 (2003).
- [5] C. Hess *et al.*, Phys. Rev. Lett. **90**, 197002 (2003).
- [6] M. Hofmann *et al.*, Phys. Rev. Lett. **87**, 047202 (2001).
- [7] M. Braden *et al.*, Z. Physik B **94**, 29 (1994).
- [8] M. Hofmann *et al.*, Phys. Rev. B **67**, 184502 (2003).
- [9] D. Johnston, *Normal-state magnetic properties of single-layer cuprate high-temperature superconductors and related materials* (Elsevier Science B.V., 1997).
- [10] M. Braden *et al.*, Europhys. Lett. **25**, 625 (1994).
- [11] C. Y. Chen *et al.*, Phys. Rev. B **43**, 392 (1991).